

Dicationic gemini surfactant gene delivery complexes contain cubic-lamellar mixed polymorphic phase

M. Foldvari, S. Wettig, I. Badea, R. Verrall, M. Bagonluri

College of Pharmacy and Nutrition, Drug Delivery and Pharmaceutical Nanotechnology Laboratory,
University of Saskatchewan, Saskatoon, SK. S7N 5C9; foldvari@duke.usask.ca

ABSTRACT

The characterization of structural properties of novel dicationic (gemini) surfactant-based DNA complexes as micro/nano-scale self-assembling delivery systems for cutaneous gene therapy is described and discussed as related to measured transfection efficiencies. We have identified the Pn3m cubic phase in DNA-gemini-DOPE complexes with gemini surfactants having 12, 16 and 18:1 alkyl tail length. Increasing gemini/DNA charge ratios ($\rho_{+/-}$) from 0.5 to 10 resulted in increasingly mixed (Pn3m and H_{II} or Pn3m and L) polymorphic systems with lamellar (L) features becoming more predominant. DNA-gemini complexes exhibited very weak single scattering peaks representative of gemini- plasmid particles with no long range order and low transfection efficiency. In gemini – DOPE complexes the main complex geometry is inverted hexagonal (H_{II}) at low concentrations of gemini, with weakly ordered systems (generally lamellar) observed at increased concentrations. Overall, the presence of the newly identified cubic Pn3m phase in the DNA-gemini-DOPE complexes appears to be advantageous for increased transfection efficiency.

1 INTRODUCTION


An important focus of research in the medical and pharmaceutical sciences is the treatment of genetic disorders via gene therapy. A successful therapeutic mechanism requires the transfer and subsequent expression of exogenous DNA such that a defective gene can be replaced or a missing gene added. There are two basic methods for facilitating this transfer, through the use of viral and non-viral vectors. While an ideal choice from the point of view of nature where their function is precisely to facilitate DNA transfection, the use of viral vectors suffers from problems associated with potential immunological responses and a limited size for the plasmid DNA that can successfully be transfected. Non-viral vectors (typically cationic lipid or cationic polymers¹) have the advantage of having, generally, low toxicity/immunogenicity, as well as having no limitation with regard to the size of DNA that can be delivered. From a manufacturing perspective non-viral vectors also benefit from simpler quality control, and more straightforward regulatory requirements.²

The major problem facing the application of non-viral vectors to gene therapy is a low efficiency.³

The objective of this study was to characterize the structural and physicochemical properties of novel dicationic lipid-based DNA complexes by small-angle x-ray scattering (SAXS), zeta potential and particle size analysis in order to determine the optimum parameters required for cellular transfection.

2 MATERIALS AND METHODS

A series of cationic lipid-DNA complexes based on dicationic (gemini) surfactants and other lipids of various compositions were constructed. The synthesis of the gemini surfactant compounds used are this study is detailed elsewhere⁴; their structures are illustrated in scheme 1. Transfection mixtures consisting of plasmid – gemini surfactant complexes, (PGs) and plasmid – gemini surfactant – helper lipid vesicles (PGLs – with 1mM dioleoylphosphatidylethanolamine (DOPE) as helper lipid) were prepared, by first complexing the DNA (at a concentration of 0.075 mM; 50 $\mu\text{g}/\text{mL}$) with the cationic surfactant, followed by addition of DOPE.

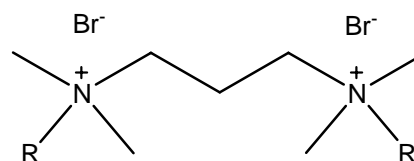

Scheme 1: General structure of the m-3-m gemini surfactants; R = dodecyl, hexadecyl, or oleyl for the 12-3-12, 16-3-16, and 18:1-3-18:1 surfactants, respectively.

Murine keratinocytes (PAM212 cell line) at 5×10^4 cells/well were grown to 60-70% confluency. The cells were transfected with PGs or PGLs containing 0.2 μg plasmid/well. The plates were incubated for 5 hours at 37°C in a CO₂ incubator. The supernatants were collected at 24 hours. The expressed protein (murine interferon γ) was determined by ELISA.

SAXS measurements were made using beamline X21 at the National Synchrotron Light Source at Brookhaven National Laboratory. The measurements were performed with 12KeV x-rays and the data covered a q-range from 0.008 \AA^{-1} to 0.5 \AA^{-1} . Samples

were loaded into 1.5 mm capillaries and the scattering pattern was recorded using a 13cm Mar CCD detector (Mar USA, Evanston, IL), at 1.26m (calibrated with the scattering pattern of silver behenate) downstream of the sample. All spectra were processed to remove background contributions by subtracting the scattering profile obtained for a water-filled capillary.

3 RESULTS

Scattering curves for each of the gemini surfactant compounds were obtained for 4 different systems (all in aqueous solution); 1) gemini alone (G), 2) gemini with plasmid (PG), 3) gemini with DOPE (GL), 4) gemini with plasmid and DOPE (PGL). Aqueous solutions of surfactant gave generally weak scattering profiles, with a sharp peak at $q = 0.156$, 0.136 , and 0.125 \AA^{-1} for the 12-3-12, 16-3-16, and 18:1-3-18:1 surfactants, respectively at concentrations of 3.75 mM.

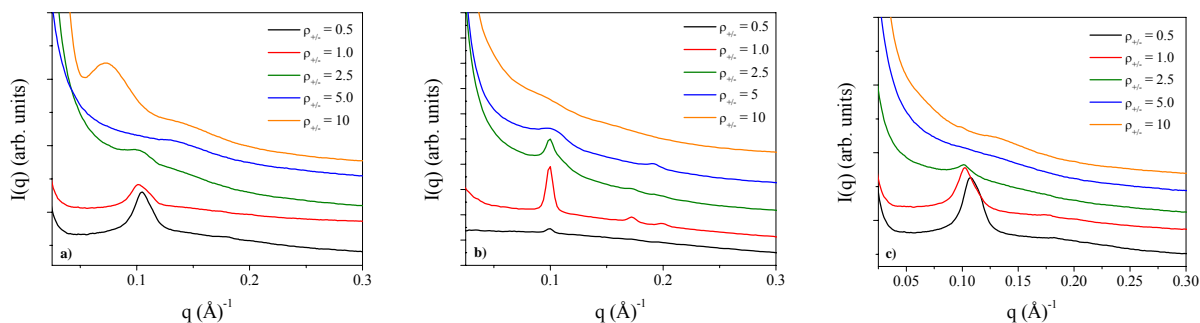


Figure 1: SAXS profiles for the gemini surfactant – DOPE (GL) systems at varying charge ratios; a) 12-3-12, b) 16-3-16, c) 18:1-3-18:1.

Table 1: SAXS Peak Positions (q) for the gemini surfactant – DOPE^a systems at varying charge ratio

Concentration	q (\AA^{-1})	d or a (\AA)	Phase	q (\AA^{-1})	d or a (\AA)	Phase	q (\AA^{-1})	d or a (\AA)	Phase
	12-3-12			16-3-16			18:1-3-18:1		
0^b	0.106	68.4	H _{II}						
	0.184								
	0.214								
0.188	0.108	67.2	H _{II}	0.100	72.5	H _{II}	0.107	67.8	H _{II}
	0.190			0.174			0.186		
				0.200			0.212		
				0.260					
0.375	0.105	69.1	H _{II}	0.099	73.3	H _{II}	0.103	70.4	H _{II}
	0.184			0.172			0.177		
				0.199			0.201		
0.938	0.101	61.2		0.101	71.8	H _{II}	0.103	61.0	
				0.173					
				0.198					
1.875	-	-	-	0.102	62.2	L	0.100	62.8	
				0.191					
3.75	0.86	73.0		0.095	66.1		0.084	74.8	
	0.180			0.153	41.1		0.155		

^a [DOPE] = 10 mM; ^b peak positions in absence of added gemini

This corresponds to average d-spacings ($d = 2\pi/q$) of 40.3, 46.2, and 50.3 Å and is consistent with the average diameter of gemini surfactant micelles as determined using dynamic light scattering.⁵⁻⁷ Solutions containing both the gemini surfactant and plasmid DNA also gave, generally, weak scattering signals. At charge ratios ($\rho_{+/-}$) of 5 and 10 a single

sharp peak is observed for both the 12-3-12 and 12-6-16 gemini surfactants with d-spacings of 45.5, and 49.1 Å, respectively, corresponding to the surfactant-complexed DNA. For the 18:1-3-18:1 surfactant, a scattering peak is observed at $\rho_{+/-} = 2.5, 5,$ and $10,$ with a d-spacing of 52.4 Å. Repeat patterns are not observed due to a lack of long range order.

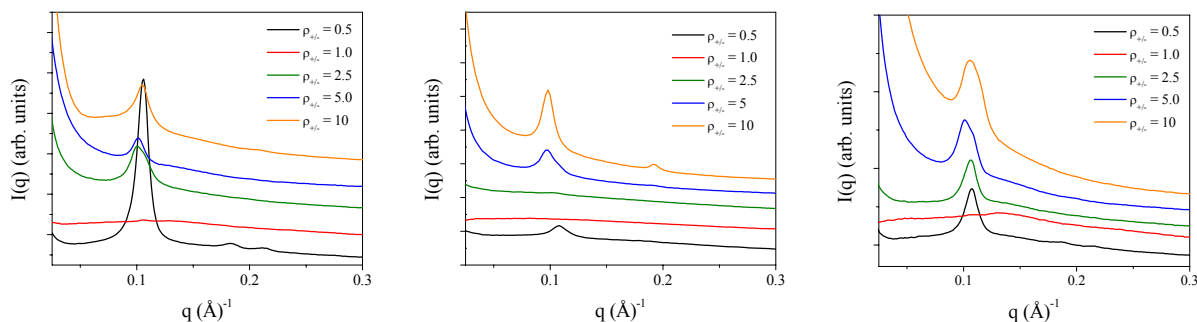


Figure 2: SAXS profiles for the plasmid – gemini surfactant – DOPE (PGL) systems at varying charge ratios; a) 12-3-12, b) 16-3-16, c) 18:1-3-18:1.

Table 2a: SAXS Peak Positions (q) for the 12-3-12 and 16-3-6 gemini surfactant – plasmid DNA – DOPE systems at varying charge ratio

$\rho_{+/-}$	q (Å ⁻¹)	Phase	hkl	d or a (Å)	$\rho_{+/-}$	q (Å ⁻¹)	Phase	hkl	d or a (Å)	$\rho_{+/-}$	q (Å ⁻¹)	Phase	hkl	d or a (Å)
12-3-12					16-3-16									
0.5	0.106	H _{II}	10	68.6	0.5	0.090	Pn3m	110	49.1	0.5	0.082	Pn3m	110	54.4
	0.115					0.108	H _{II}	10	67.3		0.106	Pn3m	111	
	0.183	H _{II}	20			0.109	Pn3m	111			0.107	L	100	67.5
	0.212	H _{II}	30			0.124	Pn3m	200			0.125	Pn3m	200	
						0.184	H _{II}	20			0.216	L	200	
						0.218	H _{II}	30						
2.5	0.082	Pn3m	110	54.1						2.5	0.097	Pn3m	110	45.6
	0.101	Pn3m	111								0.107	L	100	58.9
	0.105										0.121	Pn3m	111	
	0.129	Pn3m	200								0.199	L	200	
	0.162													
5	0.085	Pn3m	110	52.0	5	0.077	Pn3m	110	57.8	5	0.103	L	100	61.3
	0.101	Pn3m	111			0.097	Pn3m	111			0.132			
	0.102	L	100	61.8		0.099	L	100	63.6		0.166			
	0.136	Pn3m	200			0.127	Pn3m	200			0.198	L	200	
	0.201	L	200			0.189	L	200						
10	0.085	Pn3m	110	52.5	10	0.098	L	100	64.1					
	0.104	Pn3m	111			0.192	L	200						
	0.105	L	100	59.7										
	0.120	Pn3m	200											
	0.212	L	200											

